



## This MotoCAP safety rating applies to:

Brand: Macna Model: Event

Type: Jacket - Textile

Date purchased: 20 December 2018

Sizes tested: 2XL Gender: M

Style: All Purpose Test code: J18T10


## **Test Results Summary:**

	Rating	Score
MotoCAP Protection Rating	*	22.3
Abrasion	1/10	0.83
Burst	7/10	742
Impact	5/10	35.8
MotoCAP Comfort Rating	**	0.304
Moisture Vapour Resistance		41.7
Thermal Resistance		0.212
Water resistance	N/A	N/A

This garment is fitted with impact protectors for the elbows and shoulders, pockets are provided at the back for aftermarket impact protectors. Mesh panels are located in the chest, sides, inner arms and back area to allow airflow cooling in hot weather.

## **Jacket and Pants - Crash Impact Risk Zones**

This diagram is a pictorial representation of the crash impact risk Zones.

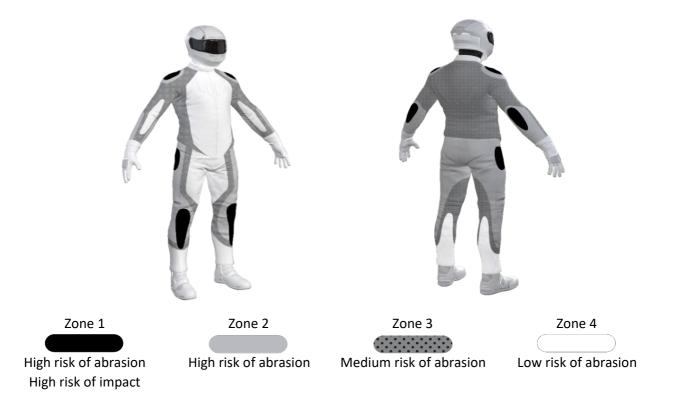



#### **Abrasion Resistance**

The garment was tested for abrasion resistance in accordance with MotoCAP test protocols. The table below shows the test results for time to abrade through all layers of the materials. Calculated for each sample by Zone, type and area coverage of each material as a proportion of that Zone.

## Details of materials used in garment:


Material A: Woven polyester fabric shell, foam layer and mesh inner liner

Material B: Woven polyester fabric shell and mesh inner liner Material C: Mesh polyester fabric shell and mesh inner liner

Zone	Coverage	Abrasion t	Average					
(%)	1	2	3	4	5	6	(seconds)	
Zone 1 and 2	areas (High abra	asion risk)						
Material A	80%	1.39	0.79	1.27	1.39	1.70	2.31	1.48 M
Material B	20%	0.69	0.56	0.49	0.91	0.63	0.65	0.65 P
Zone 3 area (I	Medium abrasio	n risk)						<u>—</u>
Material C	90%	0.68	0.45	0.38	0.57	0.42	0.48	0.50 P
Material B	10%	0.69	0.56	0.49	0.91	0.63	0.65	0.65 P
Zone 4 area (I	Low abrasion ris	sk)						
Material C	90%	0.68	0.45	0.38	0.57	0.42	0.48	0.50 M
Material B	10%	0.69	0.56	0.49	0.91	0.63	0.65	0.65 M

Abrasion times are capped at a maximum of 10.00s.

The diagram below is a visual indication of the likely abrasion performance of the materials in each zone calculated from the data in the table above. The colour coding is based on the worst performing material in each zone.

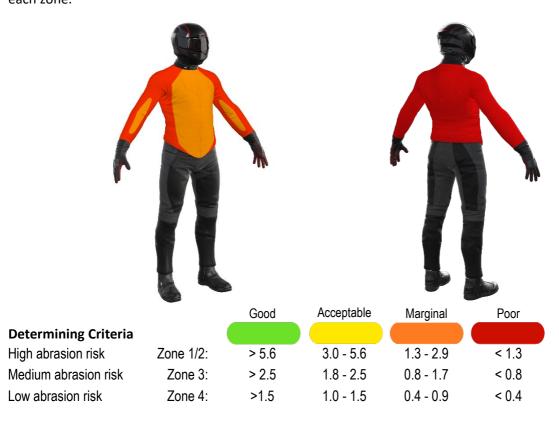




# **Burst Strength**

The garment's burst strength was tested in accordance with MotoCAP test protocols. The table below shows the burst pressure in kilopascals (kPA) for each sample tested by Zone and the average result for each zone.

# Burst pressure (kPA)

Area	1	2	3	4	5	Average
Zones 1 & 2	1560	858	340	866	884	901 A
Zone EZ	764	251	491	829	609	589 M
Zones 3 & 4	562	788	817	679	806	731 M

The diagram below illustrates the burst strength results in terms of the likely performance of the garment in an impact and is a pictorial representation of the data from the table above.

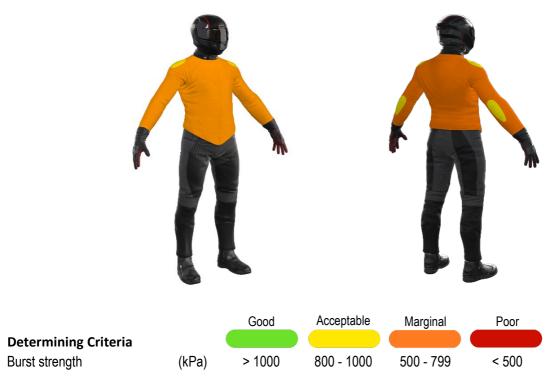



## **Impact Protection**


The garment was tested for impact protection and coverage in accordance with MotoCAP test protocols. The table below shows the test results for each strike on each impact protector in kilonewton (kN) and their area of coverage as a proportion (%) of the Zone.

Impact protector type	Elbow		Shoulder	
Average force (kN)	13.9	G	13.3	G
Maximum force (kN)	21.9	A	16.8	Α
Coverage of zone 1 area	80%		90%	<u>-</u>
Coverage of zone after displacement	60%		80%	

### Individual test results

Impact force (kN)	Elbow	Shoulder				
Strike location	Α	В	С	Α	В	С
Impact Protector 1	8.0	10.2	21.9	11.3	15.0	13.0
Impact Protector 2	10.1	13.3	19.4	9.2	14.8	13.9
Impact Protector 3	9.8	12.2	20.1	10.9	14.6	16.8

The diagram below is a visual indication of the likely performance of each impact protector calculated from the data in the table above. The colour coding is based on the worst performing score for average or maximium force for each impact zone.

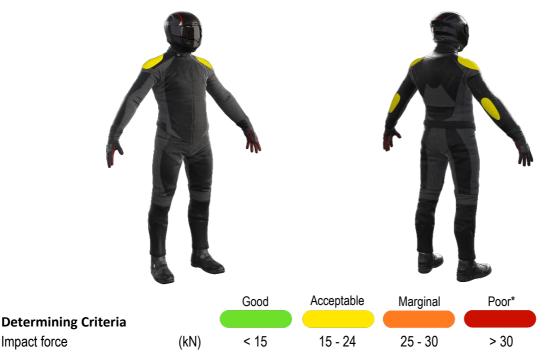

<sup>\*</sup> Poor may also indicate that no impact protector, or impact protector pocket is present in the garment

Areas shaded black are not considered in the impact protection ratings.



#### Thermal comfort

The garment was tested for thermal comfort following the MotoCAP test protocols. The table below shows the moisture vapour resistance and the thermal resistance values obtained.

	1	2	Average
Moisture Vapour Resistance - Ret	46.3	37.1	41.7
(kPam²/W)			
	1	2	Average
Thermal Resistance - R <sub>ct</sub>	0.208	0.216	0.212
(Km <sup>2</sup> /W)			

# Water spray and rain resistance

This garment has not been advertised as water resistant so has not been tested for water spray and rain resistance.