


This MotoCAP safety rating applies to:

Brand: Harley Davidson
Model: Passing Link
Type: Jacket - Leather
Date purchased: 20 January 2019
Sizes tested: L
Gender: M
Style: Cruiser
Test code: J19L06


Test Results Summary:


	Rating	Score
MotoCAP Protection Rating	★★	33.8
Abrasion	5/10	3.88
Burst	10/10	1435
Impact	1/10	0.0
MotoCAP Comfort Rating	★	0.287
Moisture Vapour Resistance		60.7
Thermal Resistance		0.291
Water resistance	N/A	N/A


This garment is not fitted with impact protectors, pockets are provided at the elbows and shoulders for aftermarket impact protectors, there is no pocket provided at the back for aftermarket impact protectors. A triple vent system is present in each side of the jacket to allow airflow cooling in hot weather. The thermal comfort measurements undertaken have not evaluated the performance of venting provided in this garment. The thermal comfort of this product may be better when the vents can be opened.


Jacket and Pants - Crash Impact Risk Zones


This diagram is a pictorial representation of the crash impact risk Zones.

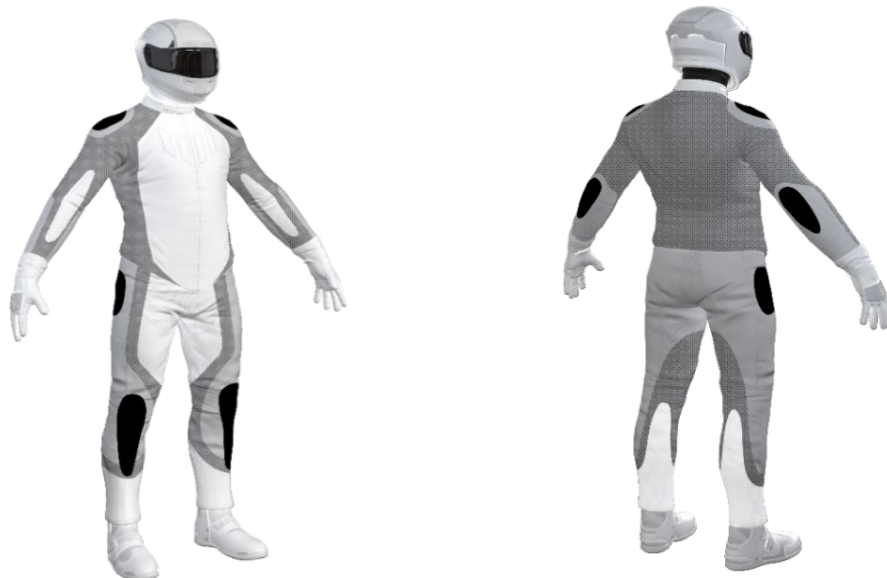

Zone 1

 High risk of abrasion
 High risk of impact

Zone 2

 High risk of abrasion

Zone 3

 Medium risk of abrasion

Zone 4

 Low risk of abrasion

Abrasion Resistance

The garment was tested for abrasion resistance in accordance with MotoCAP test protocols. The table below shows the test results for time to abrade through all layers of the materials. Calculated for each sample by Zone, type and area coverage of each material as a proportion of that Zone.

Details of materials used in garment:

Material A: Leather shell, foam layer and mesh inner liner
 Material B: Leather shell and mesh inner liner

Zone	Coverage (%)	Abrasion time for each test (seconds)						Average (seconds)	
		1	2	3	4	5	6		
Zone 1 and 2 areas (High abrasion risk)									
Material A	60%	5.11	6.19	4.54	5.33	4.76	4.90	5.14	A
Material B	40%	3.45	3.91	3.54	3.19	3.05	3.13	3.38	A
Zone 3 area (Medium abrasion risk)									
Material B	100%	3.45	3.91	3.54	3.19	3.05	3.13	3.38	G
Zone 4 area (Low abrasion risk)									
Material B	100%	3.45	3.91	3.54	3.19	3.05	3.13	3.38	G

Abrasion times are capped at a maximum of 10.00s.

The diagram below is a visual indication of the likely abrasion performance of the materials in each zone calculated from the data in the table above. The colour coding is based on the worst performing material in each zone.



Determining Criteria		Good	Acceptable	Marginal	Poor
High abrasion risk	Zone 1/2:	> 5.6	3.0 - 5.6	1.3 - 2.9	< 1.3
Medium abrasion risk	Zone 3:	> 2.5	1.8 - 2.5	0.8 - 1.7	< 0.8
Low abrasion risk	Zone 4:	> 1.5	1.0 - 1.5	0.4 - 0.9	< 0.4

Burst Strength

The garment's burst strength was tested in accordance with MotoCAP test protocols. The table below shows the burst pressure in kilopascals (kPA) for each sample tested by Zone and the average result for each zone.


Burst pressure (kPA)

Area	1	2	3	4	5	Average	
Zones 1 & 2	1628	1550	1805	1697	1273	1591	G
Zone EZ	1444	1567	992	1929	1444	1475	G
Zones 3 & 4	1011	703	1037	1436	1037	1045	G

The diagram below illustrates the burst strength results in terms of the likely performance of the garment in an impact and is a pictorial representation of the data from the table above.



Determining Criteria
Burst strength



Impact Protection

This garment was not tested for impact protection as impact protectors were not provided with the garment. The table below shows the test results for each strike on each impact protector in kilonewtons (kN) and their area of coverage as a proportion (%) of the Zone.

Impact protector type	Elbow			Shoulder		
Average force (kN)			P			P
Maximum force (kN)			P			P
Coverage of zone 1 area	0%			0%		
Coverage of zone after displacement	0%			0%		
Individual test results						
Impact force (kN)	Elbow	No impact protector present		Shoulder	No impact protector present	
Strike location	A	B	C	A	B	C
Impact Protector 1						
Impact Protector 2						
Impact Protector 3						

The diagram below is a visual indication of the likely performance of each impact protector calculated from the data in the table above. The colour coding is based on the worst performing score for average or maximum force for each impact zone.



Determining Criteria	Good	Acceptable	Marginal	Poor*
Impact force (kN)	< 15	15 - 24	25 - 30	> 30

* Poor may also indicate that no impact protector, or impact protector pocket is present in the garment

Areas shaded black are not considered in the impact protection ratings.

Thermal comfort

The garment was tested for thermal comfort following the MotoCAP test protocols. The table below shows the moisture vapour resistance and the thermal resistance values obtained.

	1	2	Average
Moisture Vapour Resistance - R_{et} ($kPam^2/W$)	58.0	63.4	60.7
	1	2	Average
Thermal Resistance - R_{ct} (Km^2/W)	0.307	0.274	0.291

Water spray and rain resistance

This garment has not been advertised as water resistant so has not been tested for water spray and rain resistance.