



This MotoCAP safety rating applies to:

Brand BMW

Model BlackLeather
Type Jacket - Leather
Date purchased 18 January 2022
Sizes tested 52 and 58

Test garment gender Male


Style All Purpose RRP \$1,000.00

Test Results Summary	Rating	Score
MotoCAP Protection Rating	****	54.0
Abrasion	8/10	5.64
Burst	10/10	1114
Impact	7/10	48.9
MotoCAP Breathability Rating	*	0.224
Moisture Vapour Resistance	-	67.8
Thermal Resistance	-	0.253
Water resistance	N/A	N/A

This garment is fitted with impact protectors for the elbows and shoulders. A pocket is provided for an aftermarket back protector. There are no vents to allow airflow movement through the garment.

Jacket and Pants - Crash Impact Risk Zones

This diagram is a pictorial representation of the crash impact risk Zones.

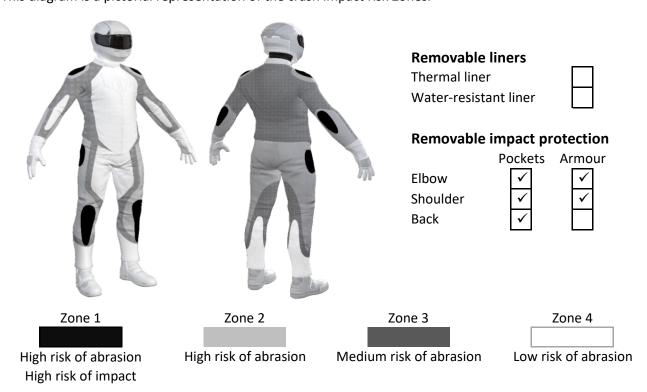



Abrasion Resistance

The jacket was tested for abrasion resistance in accordance with MotoCAP test protocols. The diagram below is a visual indication of the likely abrasion performance of the materials in each zone calculated from the data in the table below. The colour coding is based on the worst performing material in each zone.



Abrasion Resistance Performance

Abrasion rating	8/10
Abrasion score	5.64

Determining Criteria	Area	Good	Acceptable	Marginal	Poor
High abrasion risk	Zones 1 & 2	> 5.6	3.0 - 5.6	1.3 - 2.9	< 1.3
Medium abrasion risk	Zone 3	> 2.5	1.8 - 2.5	0.8 - 1.7	< 0.8
Low abrasion risk	Zone 4	>1.5	1.0 - 1.5	0.4 - 0.9	< 0.4

Individual Abrasion Resistance Results: - The table below shows the test results for time to abrade through all layers of the materials. Calculated for each sample by Zone, type and area coverage of each material as a proportion of that Zone. Abrasion times are capped at a maximum of 10.00s.

Abrasion time for each test (seconds)

Zones 1 & 2	Coverage (%)	Sample 1	Sample 2	Sample 3	Sample 4	Sample 5	Sample 6	Average	
Material A	30%	7.99	5.52	8.97	8.76	9.81	7.34	8.07	G
Material B	70%	5.16	4.66	4.84	4.73	4.16	5.71	4.88	Α
Zone 3	Coverage (%)	Sample 1	Sample 2	Sample 3	Sample 4	Sample 5	Sample 6	Average	
Material A	15%	7.99	5.52	8.97	8.76	9.81	7.34	8.07	G
Material B	85%	5.16	4.66	4.84	4.73	4.16	5.71	4.88	G
Zone 4	Coverage (%)	Sample 1	Sample 2	Sample 3	Sample 4	Sample 5	Sample 6	Average	
Material A	15%	7.99	5.52	8.97	8.76	9.81	7.34	8.07	G
Material B	85%	5.16	4.66	4.84	4.73	4.16	5.71	4.88	G

Details of materials used in jacket

Material A Quilted leather shell with fabric inner liner
Material B Leather shell with fabric inner liner



Burst Strength

The jacket was tested for burst strength in accordance with MotoCAP test protocols. The diagram below illustrates the burst strength results in terms of the likely performance of the garment in an impact and is a pictorial representation of the data from the table below.



Burst Strength Performance

Burst rating	10/10
Burst score	1114

Determining Criteria	Unit	Good	Acceptable	Marginal	Poor
Burst strength	(kPa)	> 1000	800 - 1000	500 - 799	< 500

Individual Burst Strength Results: - The table below shows the burst pressure in kilopascals (kPA) for each sample tested by Zone and the average result for each zone.

Burst pressure for each seam (kPA)

Area	Sample 1	Sample 2	Sample 3	Sample 4	Sample 5	Sample 6	Average	
Zones 1 & 2	1272	2006	881	928	834	885	1134	G
Zones 3 & 4	1423	740	708	648	1436	1235	1032	G



Impact Protection

The jacket was tested for impact protection and coverage in accordance with MotoCAP test protocols. The diagram below is a visual indication of the likely performance of each impact protector calculated from the data in the table below. The colour coding is based on the worst performing score for average or maximum force for each impact zone. Areas shaded black are not considered for impact protection ratings.



Impact Protection Performance
Impact rating 7/10
Impact score 48.9

Determining Criteria	Unit	Good	Acceptable	Marginal	Poor*
Impact force	(kN)	< 15	15 - 24	25 - 30	> 30

^{*} Poor may also indicate that no impact protector, or impact protector pocket is present in the garment

Impact Protector Results: - The table below shows the average and maximum force transmitted through each impact protector type in kilonewtons (kN) and their area of coverage as a proportion (%) of the Zone.

Impact protector type	Elbow		Shoulder
Average force (kN)	15.8	A	16.0 A
Maximum force (kN)	19.5	A	20.2 A
Coverage of Zone 1 area	95%		110%
Coverage of Zone after displacement	90%		100%

Individual Impact Protector Results: - The table below shows the test results for each strike on individual impact protectors in kilonewtons (kN) and the position of the strike. Individual strike results are capped at a maximum of 50kN.

Force transfer for each impact strike (kN)

Impact protector type	Elbow			Shoulder		
Strike location	Centre	Mid	Edge	Centre	Mid	Edge
Impact Protector 1	14.9	15.2	19.5	14.6	14.1	18.6
Impact Protector 2	16.0	13.0	17.7	15.7	14.7	20.2
Impact Protector 3	16.2	17.0	12.9	15.3	15.1	15.4



Breathability

The jacket was tested for breathability following the MotoCAP test protocols. The table below shows the moisture vapour resistance and the thermal resistance values obtained.

Without removable lin	ners	With water-resistant liner		
Breathability rating	*	Breat	hability rating	N/A
Breathability score	0.224	Breathability score		N/A
Moisture Vapour Resist	ance - R _{et} (kPa.m²/W)	1	2	Average
Without removable liners		68.8	66.8	67.8
With water-resistant liner		N/A	N/A	N/A
Thermal Resistance - R	_{ct} (K.m²/W)	1	2	Average
Without removable liners		0.265	0.241	0.253
With water-resistant liner		N/A	N/A	N/A

Water spray and rain resistance

This jacket has not been advertised as water-resistant so has not been tested for water spray and rain resistance.

Asse	ccma	nt D)etai	ilc

Brand BMW

Model BlackLeather
Type Jacket - Leather
Date purchased 18 January 2022

Tested by AMCAF, Deakin University
Report approved by MotoCAP Chief Scientist

Garment test reference J20L34
Rating first published May 2022
Rating updated 13 May 2022